

FULL PAPER

Biosynthesis of copper oxide nanoparticles using *Aspergillus niger* extract and their antibacterial and antioxidant activities

Abdulwadood Ibrahim Arif *Baquba Technical Institute, Middle Technical University, Baghdad, Iraq*

In the present study, nanoparticles of copper oxide were formed using a green approach. The Biosynthesis of CuO NPs was fabrication with the help of fungi which isolated from rot vegetables. The extract of *Aspergillus niger* fungi and Copper(II) chloride were used to synthesize bio-CuO NPs. Different techniques such as XRD (X-ray diffraction), FE-SEM (Field emission scanning electron microscopy), FTIR (Fourier transform infrared spectroscopy), and UV-Vis (UV-visible spectroscopy) were utilized to characterize and identify the biosynthesis of CuO NPs. The bioactivity of bio-CuO was screened against some types of pathogenic bacteria including *Staphylococcus aureus*, *Bacillus subtilis*, *Escherichia coli*, and *Salmonella typhimurium* via MHA (Muller Hinton agar) media. The results show that bio-CuO NPs have a potential effect against bacteria used in the current study and are more active toward *Escherichia coli* and *Salmonella Typhimurium* compared to other types. The antioxidant activity of bio-CuO was further studied in a dose-dependent manner. The obtained results show a positive effect of bio-CuO NPs and the activity increase when concentration is increased. Therefore based on the obtained results, the bio-CuO NPs have promising applications in the field of biomedical, industrial, and biological applications.

***Corresponding Author:**

Abdulwadood Ibrahim Arif

E-mail: nbb18014@mtu.edu.iq

Tel.: +96407707879018

KEYWORDSBiosynthesis of CuO; *Aspergillus niger*; pathogenic bacteria; antioxidant activity.**Introduction**

Recently, nanotechnology has been considered as one of the most widely used technologies in most fields and applications. Where they can be used in the field of industry, energy, medicine, agriculture, cosmetics, and many other applications, this technology gained its importance and advantages due to the large surface area to volume ratio, which gave it many benefits that help it to use in various fields. With the progress of science and research, the progress and development of nanotechnology

and its uses increased which often had a positive impact on the comfort and well-being of humanity [1]. Nanoparticles, especially metal oxide nanoparticles, are of great and wonderful importance that contributes to many applications because of their physical, chemical, magnetic, and other characteristics that help and contribute to their use for the benefit of humanity, the environment, food, health, and others [2]. Among metal oxide nanoparticles, are copper oxide nanoparticles, where copper is considered one of the promising elements characterized by good qualities that make it

possible to use many applications. In addition, when copper is linked to oxygen, is copper oxide formed (p-type semiconductors) and possessed an energy band gap (≈ 1.7) eV [3,4], which increases its use in several fields. When it is converted into nanoparticles, the nanoparticles of copper oxide become characterized by unique features that make them subjected to attention to be used and benefit from its advantages. Nano copper oxide has physical, chemical, electrical, optical, thermal, and many other properties that make it different from bulk material [5, 6]. It is a possession of these distinctive features facilitated its use in a wide range of applications, including catalysts [7], gas sensors [6], water pollutant removal [8], solar cells [9], and antimicrobials, anticancer [10,11] as well as many other important and useful applications summarized in reviews [12,13].

Copper oxide nanoparticles are formed by several physical or chemical methods including microwave radiation, sol-gel, thermal decomposition, solid-state reactions, precipitation, co-precipitation, and many other methods [14-17]. Each of these methods has some advantages and disadvantages, but the disadvantages and drawbacks of using these methods are more than the advantages. This is due to its reliance on materials that may be harmful to users in addition to its harm to the environment, dependence sometimes on high pressure and temperature, energy consumption is sometimes large, and other disadvantages or drawbacks [18,19]. Therefore, researchers tend to prepare nanoparticles in a way that is environmentally friendly, harmless, and simple approach. The extracted plants, fungi, algae, or other green methods that rely on in the preparation of these nanoparticles and used as a reducing agent of ions metal. There are many researchers that focused on the use of plant extracts in preparation, and they elaborated extensively in this direction, Akintelu *et al.* explained in detail in their

review [18]. Using fungi in the preparation of nanoparticles does not receive much interest and research. Therefore, we focused our current research on the formation of copper oxide using fungi. Due to fungi having the capacity to prepare a variety of NP (nanoparticles) and MONPs (metal oxide nanoparticles) types through intracellular and extracellular pathways as well as quick mycelia growth, which provides a larger surface area and easy handling of biomass. Likewise, their capacity to secrete large amounts of proteins help increase the productivity of NPs and MONPs creation. Fungi have been found to be great candidates for the synthesis of NPs and MONPs in nanotechnology with a variety of potential uses in biomedicine and industry [20-22]. In the current work, *Aspergillus niger* is used to synthesize CuO NPs that are isolated from root vegetables. The CuO biosynthesis is subjected to an antibacterial test and antioxidant screening.

Materials and methods

Materials

Copper(II) chloride (CuCl_2 , 99%), Potato Dextrose Agar (PDA), Potato Dextrose Broth (PDB), and Whatman filter paper all pushed from Sigma Aldrich-Germany.

Isolation fungi and extraction

An infected onion sample was collected and inoculated in Petri plates that contain PDA (potato dextrose agar) at the temperature of 28 ± 2 °C and the appropriate conditions to grow for 7 days. *Aspergillus niger* was grown and the fungi colony was identified using optical microscopy and macroscopic features such as diameter, conidial color, colony reverse, smoothness, and monitoring growth rate. The obtained results were compared to Raper *et al.* [23]. The obtained *Aspergillus niger* was again cultured in PDB (Potato Dextrose broth) that contain Glucose, 3 gm,

Ampiclox antibiotic, 3 mL, and 300 mL of PDB was kept in suitable condition in the dark room at 28 ± 2 °C, with continued shaking (150 rpm) for one week under observation. After the incubation time, the biomass of fungi was harvested via filtration by using filter paper (Whatman No.1). After that, the filtrate was washed three to four times using sterile distilled water. The filtered mycelia biomass was added to sterile flask contain 100 ml of sterile distilled water and kept under shaking at 150 rpm for 3 hrs at room temperature. The biomass of fungi was harvested via filtration by using filter paper (Whatman No.1). The final solution of *A. niger* extract was used for the biosynthesis of CuO NPs [20,24,25].

Biosynthesis of copper oxide nanoparticles

To prepare biosynthesis of CuO, the solution CuCl_2 (3 mM/50 mL) was added to *A. niger* extract filtrate solution (50 mL) and subjected to continuous stirring at 50 C for 4 hrs with monitoring pH (10-11). The color of the solution changed to brown which indicated the formation of CuO NPs. The final solution was centrifuged at 15,000 rpm for 20 min, and after that washed using ethanol with sterile distilled water, and then dried, crushed, and annealed at 400 C for 2 hrs. [26], and kept it for further characterization

Characterization of biosynthesis copper oxide nanoparticles

X-ray diffractometer (BRUKER D2) with ($\lambda=0.15405$ nm) and Cu-K radiation was used as a source. Morphology of bio-CuO NPs was carried out using a Field Emission Scanning Electron Microscope (FESEM-FEI Nova Nano SEM 450). Fourier Transform Infrared FTIR spectroscopy (Shimadzu) was used to find out the functional groups in the range between 400 and 4000 cm^{-1} at room temperature. UV-Visible spectrometer (Jasco

UV, V-750) was used to find out the optical properties of bio-synthesized CuO.

Bioactivity of bio-CuO NPs

Antibacterial activity assay

Firstly, we prepared a stock solution of bio-CuO NP in dimethyl sulfoxide (DMSO) media, then we diluted into 4 concentrations, 50 $\mu\text{g/ml}$, 100 $\mu\text{g/ml}$, 150 $\mu\text{g/ml}$, and 200 $\mu\text{g/ml}$, respectively. Four types of bacteria such as *Staphylococcus aureus*, *Bacillus subtilis*, *Escherichia coli*, and *Salmonella typhimurium* were used to assay the bioactivity of bio-CuO NPs via the disc diffusion method [27]. The bacteria were swabbed on the Petri plates (90 mm) containing Muller Hinton agar (MHA) media with help of cotton swabs and the sterile filter discs (6 mm) containing different concentrations of bio-CuO were put carefully on the surface of the bacteria and incubation for 24 hrs at 37 °C. After incubation time, the activity of nanoparticles was evaluated by measuring the zone of inhibition (mm) and repeated three times. The mean value was taken and (DMSO) was used as a negative control, whereas Chloramphenicol used as a positive control.

Antioxidant activity assay

2,2-Diphenyl-1-picrylhydrazyl (DPPH) radical scavenging was used to assay the antioxidant of biosynthesis CuO NPs as explained in [28,29] with some modification. The different concentrations (10, 20, 30, 40, 50, 60, 70, and 80) $\mu\text{g/ml}$ of bio-CuO NPs were used. The prepared solution was kept in a dark room and shaken for 30 min. The absorption peak of samples was measured using UV-Vis spectrophotometer at $\lambda = 517$ nm. At the same time, the positive control (ascorbic acid (AC)) was used. The experiment was repeated three times and the average absorption value was taken. The percentage

of antioxidant activity was calculated using Equation (1):

$$\text{Antioxidant activity \%} = \frac{\text{Absorbance of control} - \text{absorbance of sample}}{\text{absorbance of control}} \times 100 \quad (1)$$

Results and discussion

XRD study

The bio-synthesized CuO NPs using *Aspergillus niger* were characterized via X-ray diffraction, as depicted in Figure 2. The diffraction peaks are located at 32.6°, 35.5°, 38.6°, 48.8°, 53.4°, 58.5°, 61.6°, 66.3°, 68.1°, and 72.7° corresponded to (110), (-111), (111), (-202), (020), (202), (-113), (311),

(220), and (311) planes, respectively, which are consistent with JCPDS file No.05-0661 which confirmed the monoclinic structure bio-CuO NPs. The diffraction pattern shows no additional peaks were observed that indicated the success and the crystalline nature of biosynthesis CuO NPs [30]. Crystallite size of Bio-CuO NPs is calculated with the help of Debye-Scherrer Equation (2).

$$D = \frac{0.94\lambda}{\beta \cos\theta} \quad (2)$$

Where, $\lambda = 1.5418 \text{ \AA}$, β indicates to FWHM (full width at half width maximum), θ indicates to the angle of Bragg diffraction, and D is the crystal size of NPs. The average crystal size of bio-CuO NPs was calculated and is found 15 nm.

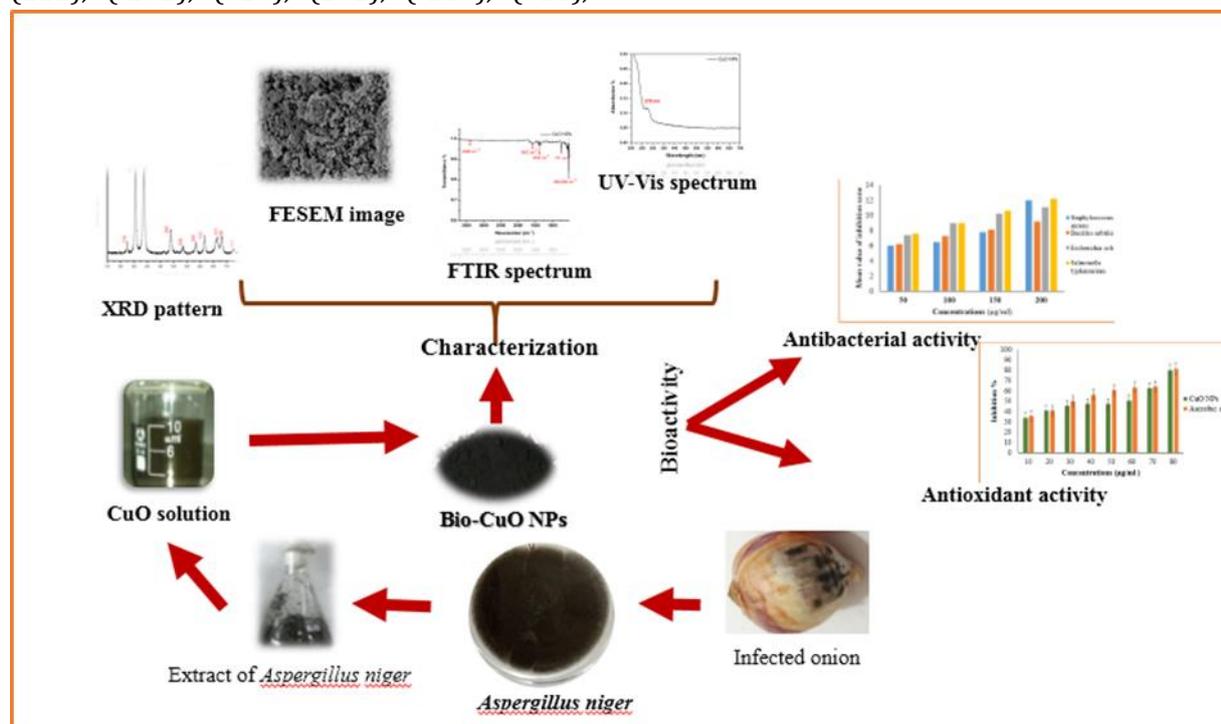


FIGURE 1 Graphical abstract

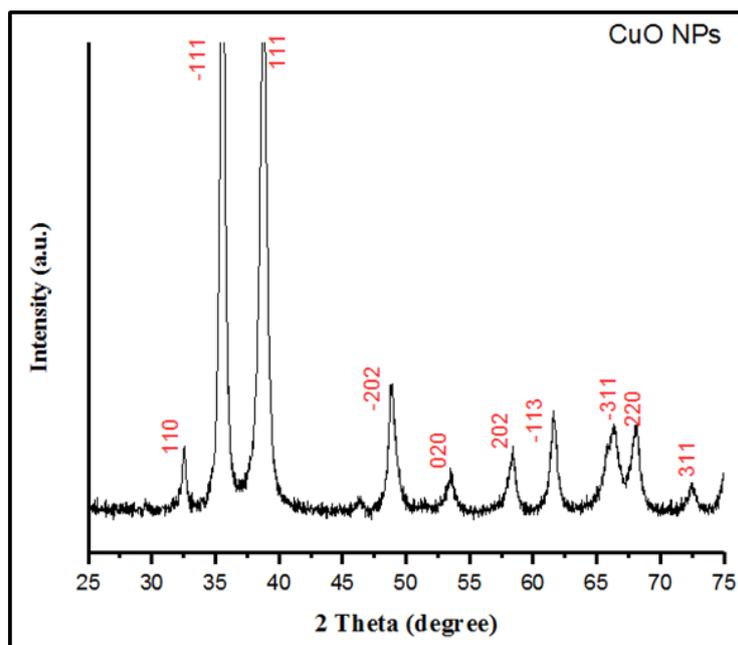


FIGURE 2 XRD of bio-CuO NPs

FESEM study

Figure 3 indicates the morphology of biosynthesis of CuO NPs was analyzed using a FESEM image. It is found from Figure 3 that

bio-CuO NPs are arranged and have a spherical-shape with uniform distribution.

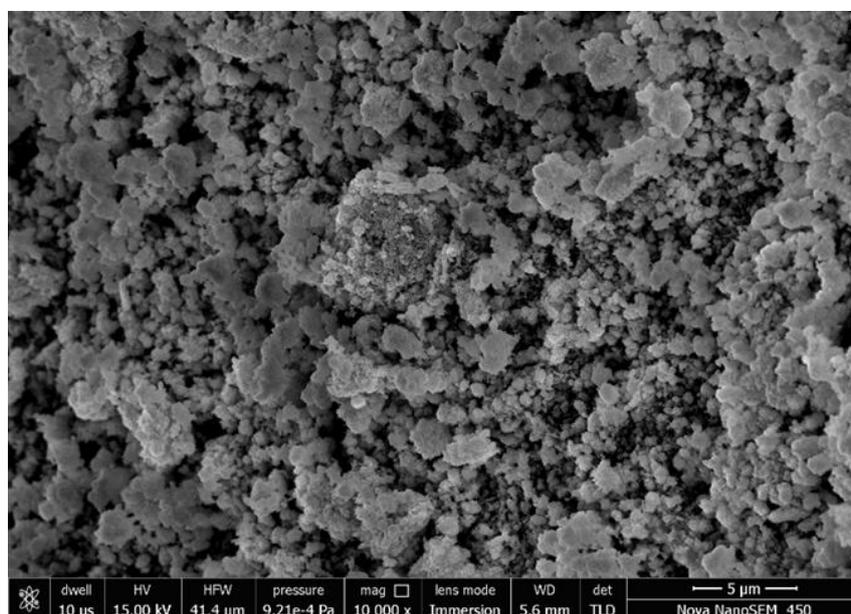


FIGURE 3 FESEM of bio-CuO NPs

FTIR study

The functional groups of biosynthesis CuO NPs were studied with a help of the FTIR

technique. Figure 4 depicts the spectrum of bio-CuO NPs. The absorbed peak at 3395 cm^{-1} is attributed to N-H stretching vibration [11,27], while a peak at 1662 cm^{-1} is

attributed to the C=O bond of an amide group [27]. The absorption peak appears at 1408 cm^{-1} assigned to C-O stretching, while the absorption peak at 741 cm^{-1} is assigned to the

C-H bond. The peaks in the range $584\text{-}500\text{ cm}^{-1}$ corresponding to metal-oxygen bond (Cu-O) [28] that confirm the success of biosynthesized nanoparticles of CuO.

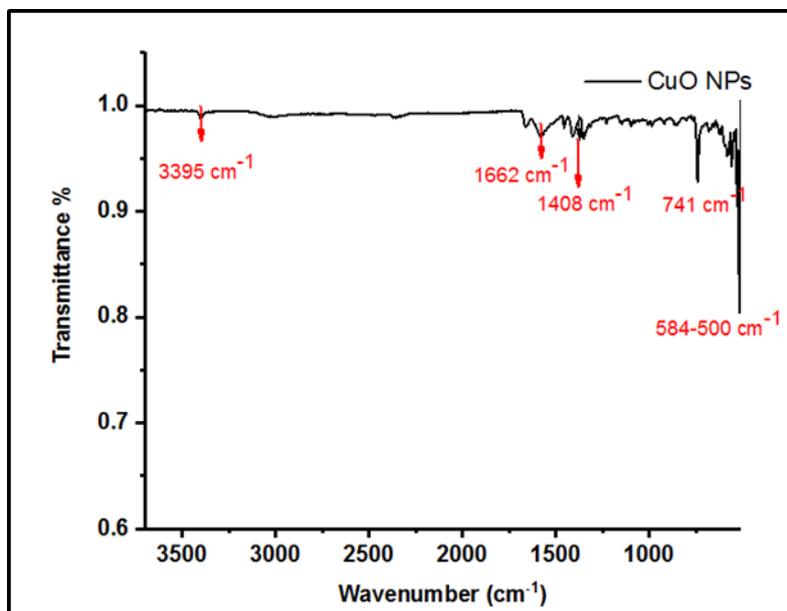


FIGURE 4 FTIR spectra of bio-CuO NPs

UV-Vis study

In this investigation, the CuO biosynthesis was confirmed using UV-Vis spectrometer. The high-intensity peak that was absorbed in

278 nm was related to the formation of nanoparticles CuO and it is in agreement with the literature of CuO NPs [31-33]. Figure 5 illustrates the absorption peaks of bio-CuO NPs.

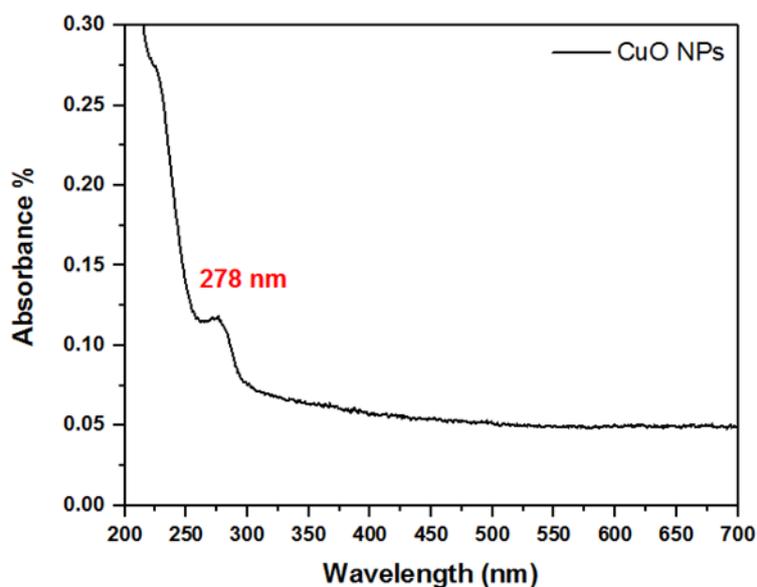


FIGURE 5 UV-Vis absorption spectra of bio-CuO NPs

*Bioactivity analysis of bio-CuO NPs**Antibacterial activity analysis*

The activity of bio-CuO NPs was examined against some types of bacteria. The zone of inhibition was measured after 24 hours in a dose-dependent manner. The results are presented in Table 1 and shown in Figure 6. Bio-CuO possesses excellent activity against different types of bacteria, as explained in different reports [5,34,35,36]. The increased concentrations of samples also lead to an increase in the inhibitory.

Nanoparticles prepared in greenways play a major role in their use as antibacterial, due

to the ability of these nanoparticles to penetrate the cell wall and inhibit their work. The nanoparticles mechanism especially copper oxide nanoparticles which used in this study lies in their ability to release some positively charged ions (Cu^{+2}) that accelerate to adhere to the negatively charged bacterial cell wall. This is might due to the electrostatic phenomenon, an attractive force occurs between the released ions and cell wall, which leads to tearing this wall and inhibiting the activity of bacteria and sometimes to their death [34,35]. In addition, the nano-size of nanoparticles which have the ability to penetrate the membrane cell of bacteria (micrometers).

TABLE 1 Antibacterial activity of bio-CuO nanoparticles at different concentrations

Type of bacteria	Mean value of inhibition zone				
	Chloramphenico 1100 ($\mu\text{g}/\text{mL}$)	50 ($\mu\text{g}/\text{mL}$)	100 ($\mu\text{g}/\text{mL}$)	150 ($\mu\text{g}/\text{mL}$)	200 ($\mu\text{g}/\text{mL}$)
<i>Staphylococcus aureus</i>	17.3	6	6.5	7.8	12
<i>Bacillus subtilis</i>	12.1	6.2	7.3	8.1	9.2
<i>Escherichia coli</i>	14.3	7.4	9	10.2	11.1
<i>Salmonella typhimurium</i>	18.7	7.6	9	10.6	12.2

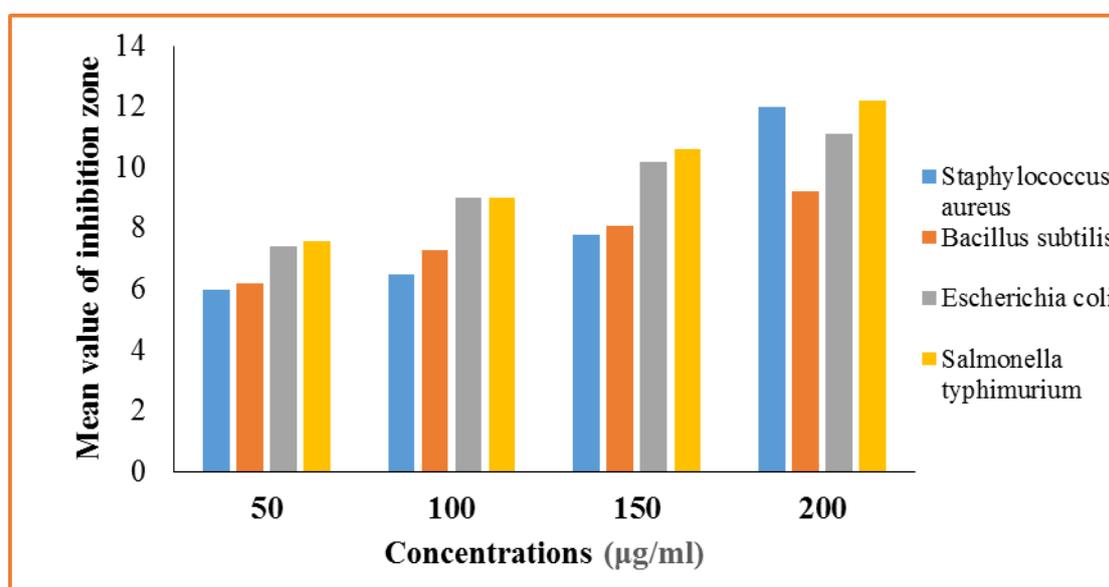


FIGURE 6 Antibacterial activity of bio-CuO nanoparticles

Antioxidant activity analysis

One of the most significant fundamental investigations of nanomaterials is anti-oxidative activity. All life systems depend heavily on antioxidants and free radicals are created in biological systems when biomolecules interact with molecule oxygen [38].

The antioxidant activity (inhibition %) of bio-CuO NPs using DPPH radical is demonstrated in Figure 7. The activity of nanoparticles was studied in a dosing method by increasing the nanoparticles concentration

of copper oxide. The % of inhibition shows an increase in the inhibitory as (33.80%, 40.63%, 45.18%, 47.27%, 47.35%, 50.51%, 62.66%, and 80.04%) when the concentration of bio-CuO increment as (10, 20, 30, 40, 50, 60, 70, and 80) $\mu\text{g/ml}$. From the Figure (7), the ability of bio-CuO to scavenge free radicals can be observed and it is very near to the stander AC [22,37,39]. At the high concentration, the CuO exhibited high activity to scavenge free radicals reach to 81%.

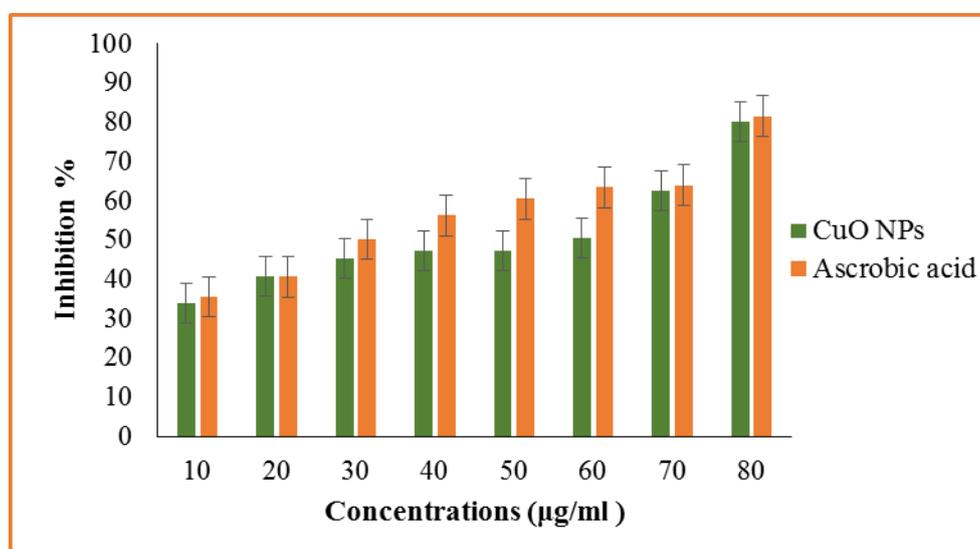


FIGURE 7 Antioxidant activity of bio-CuO nanoparticles

Conclusion

The green methods are simple, low-cost, and eco-friendly methods. Bio-CuO nanoparticles in 15 nm in crystal size with a spherical shape were synthesized using an extract of *Aspergillus niger* fungi. The formation of bio-CuO NPs was identified via different techniques. Bio-CuO confirmed their activities when examined against some kinds of bacteria and antioxidant tests. Antibacterial property revealed good activity toward bacterial under-investigated. The analysis of antioxidants shows the ability of bio-CuO to free radical scavenging. These bioactivities of bio-CuO NPs make them applicable to use

various bio-applications and packaging of food.

Acknowledgements

I would like to give my great thanks to all laboratory technicians who helping me to complete the practical part of my work.

Conflict of Interest

The author declared there is no conflict of interest.

Orcid:

Abdulwadood Ibrahim Arif:

<https://orcid.org/0000-0002-4299-0722>

References

- [1] H. Alishah, S. Pourseyedi, S.Y. Ebrahimipour, S.E. Mahani, N. Rafiei, Green synthesis of starch-mediated CuO nanoparticles: preparation, characterization, antimicrobial activities and in vitro MTT assay against MCF-7 cell line, *Rendiconti Lincei*, **2017**, *28*, 65-71. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [2] Z. Alhalili, Green synthesis of copper oxide nanoparticles CuO NPs from Eucalyptus Globulus leaf extract: Adsorption and design of experiments, *Arab. J. Chem.*, **2022**, *15*, 103739. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [3] L. Debbichi, M.C. Marco de Lucas, J.F. Pierson, P. Kruger, Vibrational properties of CuO and Cu₄O₃ from first-principles calculations, and Raman and infrared spectroscopy, *J. Phys. Chem. C*, **2012**, *116*, 10232-10237. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [4] A. Tadjarodi, R. Roshani, A green synthesis of copper oxide nanoparticles by mechanochemical method, *Curr. Chem. Lett.*, **2014**, *3*, 215-220. [[Pdf](#)], [[Google Scholar](#)], [[Publisher](#)]
- [5] S. Sukumar, A. Rudrasenan, D. Padmanabhan Nambiar, Green-synthesized rice-shaped copper oxide nanoparticles using Caesalpinia bonducella seed extract and their applications, *ACS omega*, **2020**, *5*, 1040-1051. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [6] J. Zhu, H. Bi, Y. Wang, X. Wang, X. Yang, L. Lu, Synthesis of flower-like CuO nanostructures via a simple hydrolysis route, *Mater. Lett.*, **2007**, *61*, 5236-5238. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [7] W. Zhang, F. Guo, F. Wang, N. Zhao, L. Liu, J. Li, Z. Wang, Synthesis of quinazolines via CuO nanoparticles catalyzed aerobic oxidative coupling of aromatic alcohols and amidines, *Org. Biomol. Chem.*, **2014**, *12*, 5752-5756. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [8] J. Peternela, M.F. Silva, M.F. Vieira, R. Bergamasco, A.M.S. Vieira, Synthesis and impregnation of copper oxide nanoparticles on activated carbon through green synthesis for water pollutant removal, *Mat. Res.*, **2017**, *21*, e20160460. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [9] J.K. Sharma, M.S. Akhtar, S. Ameen, P. Srivastava, G. Singh, Green synthesis of CuO nanoparticles with leaf extract of *Calotropis gigantea* and its dye-sensitized solar cells applications, *J. Alloys Compd.*, **2015**, *632*, 321-325. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [10] P.C. Nagajyothi, P. Muthuraman, T.V.M. Sreekanth, D.H. Kim, J. Shim, Green synthesis: in-vitro anticancer activity of copper oxide nanoparticles against human cervical carcinoma cells, *Arab. J. Chem.*, **2017**, *10*, 215-225. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [11] V. Gnanavel, V. Palanichamy, S.M. Roopan, Biosynthesis and characterization of copper oxide nanoparticles and its anticancer activity on human colon cancer cell lines (HCT-116), *J. Photochem. Photobiol. B, Biol.*, **2017**, *171*, 133-138. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [12] H.N. Cuong, S. Pansambal, S. Ghotekar, R. Oza, N.T.T. Hai, N.M. Viet, V.H. Nguyen, New frontiers in the plant extract mediated biosynthesis of copper oxide (CuO) nanoparticles and their potential applications: A review, *Environ. Res.*, **2022**, *203*, 111858. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [13] N. Verma, N. Kumar, Synthesis and biomedical applications of copper oxide nanoparticles: an expanding horizon, *ACS Biomater. Sci. Eng.*, **2019**, *5*, 1170-1188. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [14] H. Wang, J.Z. Xu, J.J. Zhu, H.Y. Chen, Preparation of CuO nanoparticles by microwave irradiation, *J. Cryst. Growth*, **2002**, *244*, 88-94. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [15] D.I. Son, C.H. You, T.W. Kim, Structural, optical, and electronic properties of colloidal CuO nanoparticles formed by using a colloid-thermal synthesis process, *Appl. Surf. Sci.*, **2009**, *255*, 8794-8797. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]

- [16] B. Arunkumar, S.J. Jeyakumar, M. Jothibas, A sol-gel approach to the synthesis of CuO nanoparticles using Lantana camara leaf extract and their photo catalytic activity, *Optik*, **2019**, *183*, 698-705. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [17] J.E. Jeronsia, L.A. Joseph, P.A. Vinosha, A.J. Mary, S.J. Das, Camellia sinensis leaf extract mediated synthesis of copper oxide nanostructures for potential biomedical applications, *Mater. Today: Proc.*, **2019**, *8*, 214-222. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [18] S.A. Akintelu, A.S. Folorunso, F.A. Folorunso, A.K. Oyebamiji, Green synthesis of copper oxide nanoparticles for biomedical application and environmental remediation, *Heliyon*, **2020**, *6*, e04508. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [19] K. Velsankar, S. Suganya, P. Muthumari, S. Mohandoss, S. Sudhahar, Ecofriendly green synthesis, characterization and biomedical applications of CuO nanoparticles synthesized using leaf extract of Capsicum frutescens, *J. Environ. Chem. Eng.*, **2021**, *9*, 106299. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [20] V.N. Kalpana, B.A.S. Kataru, N. Sravani, T. Vigneshwari, A. Panneerselvam, V.D. Rajeswari, Biosynthesis of zinc oxide nanoparticles using culture filtrates of Aspergillus niger: Antimicrobial textiles and dye degradation studies, *OpenNano*, **2018**, *3*, 48-55. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [21] V.F. Consolo, A. Torres-Nicolini, V.A. Alvarez, (). Mycosynthetized Ag, CuO and ZnO nanoparticles from a promising Trichoderma harzianum strain and their antifungal potential against important phytopathogens, *Sci. Rep.*, **2020**, *10*, 1-9. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [22] V.M. Mani, S. Kalaivani, S. Sabarathinam, M. Vasuki, A.J.P.G. Soundari, M.A. Das, A. Elfasakhany, A. Pugazhendhi, Copper oxide nanoparticles synthesized from an endophytic fungus Aspergillus terreus: Bioactivity and anti-cancer evaluations, *Environ. Res.*, **2021**, *201*, 111502. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [23] A.M. Mardanova, G.F. Hadieva, M.T. Lutfullin., I.V. Khilyas, L.F. Minnullina, A.G. Gilyazeva, L.M. Bogomolnaya, M.R. Sharipova, *Bacillus subtilis* Strains with Antifungal Activity against the Phytopathogenic Fungi, *Agricultural Sciences*, **2017**, *8*, 1-20. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [24] A.M. Suood, M.K. Saleh, K.M. Thalij, (2021, November). Synthesis of copper nanoparticles using Aspergillus niger and their efficacy against pathogenic staphylococcus aureus, *IOP Conference Series: Earth and Environmental Science*, **2021**, *910*, 012083. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [25] E. Rasha, M.M. Alkhulaifi, M. AlOthman, I. Khalid, E. Doaa, K. Alaa, M.A. Awad, Abdalla, Effects of zinc oxide nanoparticles synthesized using Aspergillus niger on Carbapenem-Resistant Klebsiella pneumonia in vitro and in vivo, *Front. Cell. Infect. Microbiol.*, **2021**, *11*, 748739. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [26] M.A. Amin, M.M. EL-Aasser, S.M. Ayoub, H.H. EL-Shiekh, T.M. Sakr, Exploitation of Aspergillus flavus synthesized copper oxide nanoparticles as a novel medical agent. *J. Radioanal. Nucl. Chem.*, **2021**, *328*, 299-313. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [27] F. Amin, B. Khattak, A. Alotaibi, M. Qasim, I. Ahmad, R. Ullah, M. Bourhia, A. Gul, S. Zahoor, R. Ahmad, Green synthesis of copper oxide nanoparticles using Aerva javanica leaf extract and their characterization and investigation of in vitro antimicrobial potential and cytotoxic activities, *Evid. Based Complementary Altern. Med.*, **2021**, *2021*, 5589703. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [28] R. Dobrucka, Antioxidant and catalytic activity of biosynthesized CuO nanoparticles using extract of Galeopsis herba, *J. Inorg. Organomet. Polym. Mater.*, **2018**, *28*, 812-819. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]

- [29] W. Brand-Williams, M.E. Cuvelier, C.L.W.T. Berset, Use of a free radical method to evaluate antioxidant activity, *LWT - Food Sci. Technol.*, **1995**, *28*, 25-30. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [30] N.M. Basith, J.J. Vijaya, L.J. Kennedy, M. Bououdina, Structural, morphological, optical, and magnetic properties of Ni-doped CuO nanostructures prepared by a rapid microwave combustion method, *Mater. Sci. Semicond. Process.*, **2014**, *17*, 110-118. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [31] R. Sankar, R. Maheswari, S. Karthik, K.S. Shivashangari, V. Ravikumar, Anticancer activity of *Ficus religiosa* engineered copper oxide nanoparticles, *Mater. Sci. Eng. C*, **2014**, *44*, 234-239. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [32] P. Narasaiah, B.K. Mandal, N.C. Sarada, (2017, November). Biosynthesis of copper oxide nanoparticles from *Drypetes sepiaria* leaf extract and their catalytic activity to dye degradation, *IOP conference series: materials science and engineering*, **2017**, *263*, 022012. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [33] P. Sutradhar, M. Saha, D. Maiti, Microwave synthesis of copper oxide nanoparticles using tea leaf and coffee powder extracts and its antibacterial activity, *J. Nanostructure Chem.*, **2014**, *4*, 1-6. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [34] H.R., Naika, K. Lingaraju, K. Manjunath, D. Kumar, G. Nagaraju, D. Suresh, H. Nagabhushana, Green synthesis of CuO nanoparticles using *Gloriosa superba* L. extract and their antibacterial activity, *J. Taibah Univ. Sci.*, **2015**, *9*, 7-12. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [35] T. Pandiyarajan, R. Udayabhaskar, S. Vignesh, R.A. James, B. Karthikeyan, Synthesis and concentration dependent antibacterial activities of CuO nanoflakes, *Mater. Sci. Eng. C*, **2013**, *33*, 2020-2024. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [36] A. Azam, A.S. Ahmed, M. Oves, M.S. Khan, A. Memic, Size-dependent antimicrobial properties of CuO nanoparticles against Gram-positive and-negative bacterial strains, *Int. J. Nanomedicine*, **2012**, *7*, 3527-3535. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [37] P. Peddi, P.R. Ptsrk, N.U. Rani, S.L. Tulasi, Green synthesis, characterization, antioxidant, antibacterial, and photocatalytic activity of *Suaeda maritima* (L.) Dumort aqueous extract-mediated copper oxide nanoparticles, *J. Genet. Eng. Biotechnol.*, **2021**, *19*, 1-11. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [38] A. Muthuvel, M. Jothibas, C. Manoharan, Synthesis of copper oxide nanoparticles by chemical and biogenic methods: photocatalytic degradation and in vitro antioxidant activity, *Nanotechnol. Environ. Eng.*, **2020**, *5*, 1-19. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [39] K. Velsankar, A.K. RM, R. Preethi, V. Muthulakshmi, S. Sudhahar, Green synthesis of CuO nanoparticles via *Allium sativum* extract and its characterizations on antimicrobial, antioxidant, antilarvicidal activities, *J. Environ. Chem. Eng.*, **2020**, *8*, 104123. [[crossref](#)], [[Google Scholar](#)], [[Publisher](#)]

How to cite this article: Abdulwadood Ibrahim Arif*. Biosynthesis of copper oxide nanoparticles using *Aspergillus niger* extract and their antibacterial and antioxidant activities. *Eurasian Chemical Communications*, 2023, 5(7), 598-608. **Link:** http://www.echemcom.com/article_168762.html